

BS 3692:2014



BSI Standards Publication

ISO metric precision hexagon bolts, screws and nuts – Specification

Publishing and copyright information

The BSI copyright notice displayed in this document indicates when the document was last issued.

© The British Standards Institution 2014

Published by BSI Standards Limited 2014

ISBN 978 0 580 83041 9

ICS 21.060.10; 21.060.20

The following BSI references relate to the work on this document:

Committee reference FME/9

Draft for comment 14/30283396 DC

Publication history

First published December 1963

Second edition, August 1967

Third edition, February 2001

Fourth (present) edition, October 2014

Amendments issued since publication

Date	Text affected

Contents

Foreword *iii*

1	Scope	1
2	Normative references	1
3	Information and requirements to be agreed and documented	2
4	General dimensions	3
5	Length of bolts and screws	3
6	Ends of bolts and screws	4
7	Screw threads	5
8	Length of thread on bolts and screws	5
9	Dimensions of bolts and screws	6
10	Angularity and eccentricity of bolts, screws and nuts	11
11	Dimensions of nuts	11
12	Chamfering, washer facing and countersinking bolts, screws and nuts	17
13	Material and manufacture of steel bolts and screws	17
14	Mechanical properties of steel bolts and screws	18
15	Strength grade designation system for steel nuts	19
16	Material and manufacture of steel nuts	19
17	Mechanical properties of steel nuts (excluding thin nuts)	20
18	Drilled bolts with split pin holes	23
19	Finishes	23
20	Marking and identification	23
21	Inspection and testing	24

Annexes

Annex A (informative)	Strength grade designation system for steel bolts and screws	25
Annex B (informative)	Recommended gauge for checking squareness of thread to face of nut	25
Annex C (normative)	Testing of mechanical properties of steel nuts	26
Annex D (informative)	Association of bolt and screw lengths and diameters (see Clause 8)	27
Annex E (informative)	Basis for the derivation of tolerances	33
Annex F (informative)	Manufacturer's recommended range of sizes	38

Bibliography 40

List of figures

Figure 1	Rounded end	5
Figure 2	Rolled thread end	5
Figure 3	Hexagon head bolt, washer-faced	6
Figure 4	Hexagon head screw, washer-faced	7
Figure 5	Full bearing head	7
Figure 6	Normal thickness nut	11
Figure 7	Thin nut	12
Figure 8	Enlarged view of nut countersunk	12
Figure 9	Slotted nut. Sizes M4 to M39 only (six slots)	15
Figure 10	Castle nut. Sizes M12 to M39 only (six slots)	15
Figure 11	Castle nut. Sizes M42 to M68 only (eight slots)	15
Figure 12	Depth of decarburization on steel bolts and screws	18
Figure B.1	Nut squareness gauge	25
Figure C.1	Proof load test for nut	26
Figure E.1	Widths across flats	33
Figure E.2	Widths across corners	33
Figure E.3	Heights of heads	33
Figure E.4	Shank diameter of full size bolts	33
Figure E.5	Nominal length	34
Figure E.6	Thread lengths	34
Figure E.7	Eccentricity of the head	34

Figure E.8 – Angularity of the head	34
Figure E.9 – Eccentricity between shank and thread	34
Figure E.10 – Eccentricity of split pin hole	35
Figure E.11 – Widths across flats	35
Figure E.12 – Widths across corners	35
Figure E.13 – Thicknesses of nuts	36
Figure E.14 – Dimensions of slots	36
Figure E.15 – Eccentricity of the hexagon	36
Figure E.16 – Eccentricity of the slots	37
Figure E.17 – Angularity of the nuts	37

List of tables

Table 1 – Tolerances on the standard nominal lengths of bolts and screws	4
Table 2 – Thread tolerance classes	5
Table 3 – Basis for standard thread lengths	5
Table 4a – ISO metric precision hexagon bolts and screws	8
Table 4b – ISO metric precision hexagon bolts and screws	9
Table 5 – ISO metric precision hexagon nuts and thin nuts	13
Table 6 – ISO metric precision hexagon slotted nuts and castle nuts	16
Table 7 – Strength grade designation of steel nuts	19
Table 8 – Recommended bolt and nut combinations	19
Table 9 – Chemical composition of steel nuts	20
Table 10 – Mechanical properties of steel nuts	20
Table 11 – Proof loads for steel nuts (coarse pitch series)	21
Table 12 – Finishes	23
Table 13 – Marking of nuts	24
Table A.1 — Strength grade designations of steel bolts and screws	25
Table D.1a – Preferred standard sizes of ISO metric precision hexagon bolts and screws	28
Table D.1b – Preferred standard sizes of ISO metric precision hexagon bolts and screws	30
Table D.2 – Standard thread lengths and the shortest lengths designated as bolts, related to diameter	32
Table F.1 – Hexagon head bolts	38
Table F.2 – Hexagon head screws	39

Summary of pages

This document comprises a front cover, an inside front cover, pages i to iv, pages 1 to 40, an inside back cover and a back cover.

Foreword

Publishing information

This British Standard is published by BSI Standards Limited, under licence from The British Standards Institution, and came into effect on 31 October 2014. It was prepared by Technical Committee FME/9, *Nuts and accessories*. A list of organizations represented on this committee can be obtained on request to its secretary.

Supersession

This British Standard supersedes BS 3692:2001, which is withdrawn.

Relationship with other publications

This British Standard should be read in conjunction with BS EN ISO 898-1 as it contains tables that reflect up-to-date best practice for mechanical properties of bolts.

Information about this document

The mechanical properties of the nuts in this British Standard do not conform to BS EN ISO 898-2. Higher proof load values have been allocated to the revised property classes in BS EN ISO 898-2 in order to ensure that fracture of the bolt generally occurs in the case of overloading.

CAUTION. Nuts in accordance with this standard cannot be fully loaded with sufficient assurance up to the yield point of the appropriate bolt, or beyond this, without the possibility of the nut thread being stripped, and for this reason it is essential that new designs of nuts for use with BS 3692 bolts and studs conforming to this standard conform to BS EN ISO 898-2.

In order to differentiate nuts that conform to this British standard from those that conform to BS EN ISO 898-2 vertical bars have been added to the symbols for strength grade designations e.g. l8l instead of 8.

It has been assumed in the preparation of this British Standard that the execution of its provisions will be entrusted to appropriately qualified and experienced people, for whose use it has been produced.

Presentational conventions

The provisions of this standard are presented in roman (i.e. upright) type. Its requirements are expressed in sentences in which the principal auxiliary verb is "shall".

Commentary, explanation and general informative material is presented in smaller italic type, and does not constitute a normative element.

Requirements in this standard are drafted in accordance with *Rules for the structure and drafting of UK standards*, subclause J.1.1, which states, "Requirements should be expressed using wording such as: 'When tested as described in Annex A, the product shall ...'". This means that only those products that are capable of passing the specified test will be deemed to conform to this standard.

Contractual and legal considerations

This publication does not purport to include all the necessary provisions of a contract. Users are responsible for its correct application.

Compliance with a British Standard cannot confer immunity from legal obligations.

1 Scope

This standard gives the general dimensions and tolerances of precision hexagon bolts, screws and nuts with ISO metric threads in diameters from 1.6 mm to 68 mm inclusive.

This standard specifies mechanical properties of bolts, screws and nuts made of carbon steel and alloy steel when tested at an ambient temperature range of 10 °C to 35 °C.

NOTE 1 Fasteners (the term used when bolts, screws and nuts are considered all together) that conform to the requirements of this standard are evaluated at this ambient temperature range. They might not retain the specified mechanical and physical properties at elevated temperatures and/or lower temperatures.

This standard is not applicable to fasteners used in applications outside of the range –50 °C to +150 °C.

NOTE 2 Fasteners conforming to the requirements of this standard are used in applications ranging from –50 °C to +150 °C. The use of fasteners in applications outside of this range, and up to a maximum temperature of +300 °C, might need to be based on the advice of an experienced fastener metallurgist for determining appropriate choices for a given application.

NOTE 3 Nuts in accordance with this standard cannot be fully loaded with sufficient assurance up to the yield point of the appropriate bolt, or beyond this, without the possibility of the nut thread being stripped, and for this reason it is essential that new designs of nuts for use with BS 3692 bolts and studs conforming to this standard conform to BS EN ISO 898-2.

NOTE 4 Nuts with an effective height of less than 0.6d and/or with a width across flats or outside diameter of less than 1.4d are excluded from the mechanical requirements specified.

The dimensional requirements of this British Standard are also applicable to non-ferrous and stainless steel bolts, screws and nuts.

Information on strength grade designation system for steel bolts and screws can be found in Annex A.

NOTE 5 The range of nominal sizes included in this British Standard is likely to be adequate for most of the applications for which this series is likely to be employed, but for the convenience of users requiring larger sizes, further information in relation to the derivation of tolerances is in Annex E.

NOTE 6 In addition to the definitive requirements, this standard also requires the items detailed in Clause 3 to be documented. For compliance with this standard, both the definitive requirements and the documented items have to be met.

2 Normative references

The following documents, in whole or in part, are normatively referenced in this document and are indispensable for its application. For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

BS 3643-1, *ISO metric screw threads – Part 1: Principles and basic data*

BS 3643-2, *ISO metric screw threads – Part 2: Specification for selected limits of size*

BS EN ISO 898-1:2013, *Mechanical properties of fasteners made of carbon steel and alloy steel – Part 1: Bolts, screws and studs with specified property classes – coarse thread and fine pitch thread*

BS EN ISO 1234, *Split pins*

BS EN ISO 4042, *Fasteners – Electroplated coatings*

BS EN ISO 4759-1:2001, *Tolerances for fasteners – Part 1: Bolts, screws, studs and nuts – Product grades A, B and C*

BS EN ISO 6506-1, *Metallic materials – Brinell hardness test – Part 1: Test method*

BS EN ISO 6506-2, *Metallic materials – Brinell hardness test – Part 2: Verification and calibration of testing machines*

BS EN ISO 6506-3, *Metallic materials – Brinell hardness test – Part 3: Calibration of reference blocks*

BS EN ISO 6506-4, *Metallic materials – Brinell hardness test – Part 4: Table of hardness values*

BS EN ISO 6507-1, *Metallic materials – Vickers hardness test – Part 1: Test method*

BS EN ISO 6507-2, *Metallic materials – Vickers hardness test – Part 2: Verification and calibration of testing machines*

BS EN ISO 6507-3, *Metallic materials – Vickers hardness test – Part 3: Calibration of reference blocks*

BS EN ISO 6507-4, *Metallic materials – Vickers hardness test – Part 4: Tables of hardness values*

BS EN ISO 6508-1, *Metallic materials – Rockwell hardness test – Test method (scales A, B, C, D, E, F, G, H, K, N, T)*

BS EN ISO 6508-2, *Metallic materials – Rockwell hardness test – Verification and calibration of testing machines (scales A, B, C, D, E, F, G, H, K, N, T)*

BS EN ISO 6508-3, *Metallic materials – Rockwell hardness test – Calibration and reference blocks (scales A, B, C, D, E, F, G, H, K, N, T)*

BS EN ISO 10684, *Fasteners – Hot dipped galvanized coatings*

BS ISO 965-5, *ISO general purpose metric screw threads – Tolerances – Limits of sizes for internal screw threads to mate with hot-dip galvanized external screw threads with maximum size of tolerance position h before galvanizing*

3 Information and requirements to be agreed and documented

3.1 Information to be supplied by the purchaser

The following information to be supplied by the purchaser shall be fully documented.

For compliance with the standard both the definitive requirements specified throughout the standard and the following documented items shall be satisfied:

- a) general product description, i.e. “bolts”, “screws”, “nuts”, “slotted nuts”, etc., and material (if other than steel);
- b) the letter “M” indicating that the product is ISO metric;
- c) the nominal size (thread diameter) of the product in mm;
- d) the nominal length of bolts and screws in mm;
- e) the number of this British Standard e.g. BS 3692;
- f) the strength grade symbol;
- g) whether bolts with split pin holes are required (see 18.1);
- h) whether bolts, screws or nuts should be coated, and the type of coating to be used (see Clause 19).

EXAMPLE

Bolts 10 mm diameter, 50 mm long, manufactured from steel of strength grade 8.8, would be designated:

“Bolts M10 × 50, 8.8 to BS 3692”.

Nuts 12 mm in diameter, manufactured from steel of strength grade 6, zinc plated, would be designated:

“Nuts M12, 6 to BS 3692, zinc plated to BS EN ISO 4042”.

3.2 Items to be agreed between the manufacturer and purchaser

The following items to be agreed between the contracting parties are specified in the clauses referred to and shall be fully documented. For compliance with the standard both the definitive requirements specified throughout the standard and the following documented items shall be satisfied:

- a) the tolerances on screw threads (see 7.2);
- b) whether free cutting steel is to be used for the manufacture of nuts (see 16.2);
- c) minimum hardness values for nuts which are not proof load tested (see Clause 17).

4 General dimensions

The bolts, screws and nuts shall conform to the general dimensions given in Table 1, Table 3, Table 4, Table 5, and Table 6, and in Clause 5 to Clause 12.

5 Length of bolts and screws**5.1 Nominal length**

The nominal length of a bolt or screw shall be the distance from the underside of the head to the extreme end of the thread including any chamfer or radius.

The standard nominal lengths shall be in accordance with Table 1.

NOTE Preferred nominal lengths of bolts and screws, in association with diameters, are given in Annex D.

5.2 Tolerance on length

The tolerance on the nominal length shall in accordance with Table 1.

Table 1 Tolerances on the standard nominal lengths of bolts and screws

Dimensions in millimetres			
Nominal length /	Tolerance	Nominal length /	Tolerance
5	±0.24	90	±0.70
6	±0.24	(95)	±0.70
(7)	±0.29	100	±0.70
8	±0.29	(105)	±0.70
(9)	±0.29	110	±0.70
10	±0.29	(115)	±0.70
(11)	±0.35	120	±0.70
12	±0.35	(125)	±0.80
14	±0.35	130	±0.80
16	±0.35	140	±0.80
(18)	±0.35	150	±0.80
20	±0.42	160	±0.80
(22)	±0.42	170	±0.80
25	±0.42	180	±0.80
(28)	±0.42	190	±0.925
30	±0.42	200	±0.925
(32)	±0.50	220	±0.925
35	±0.50	240	±0.925
(38)	±0.50	260	±1.05
40	±0.50	280	±1.05
45	±0.50	300	±1.05
50	±0.50	325	±1.15
55	±0.60	350	±1.15
60	±0.60	375	±1.15
65	±0.60	400	±1.15
70	±0.60	425	±1.25
75	±0.60	450	±1.25
80	±0.60	475	±1.25
85	±0.70	500	±1.25

NOTE 1 Lengths shown in brackets are non-preferred.

NOTE 2 See also Annex D.

6 Ends of bolts and screws

The ends of bolts and screws shall be finished with either a 45° chamfer to a depth slightly exceeding the depths of thread, or a radius approximately equal to one and a quarter times the nominal diameter of the shank; the choice of method being at the discretion of the manufacturer.

When bolts and screws are made with rolled threads, the lead formed at the end of the bolt by the rolling operation may be regarded as providing the necessary chamfer to the end with no other machining operation being necessary, and the end shall be reasonably square with the centre line of the shank (see Figure 1 and Figure 2).

Figure 1 Rounded end


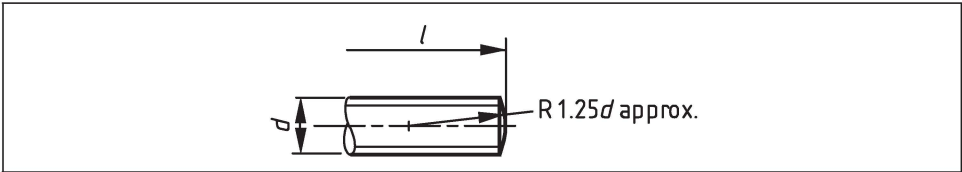


Figure 2 Rolled thread end

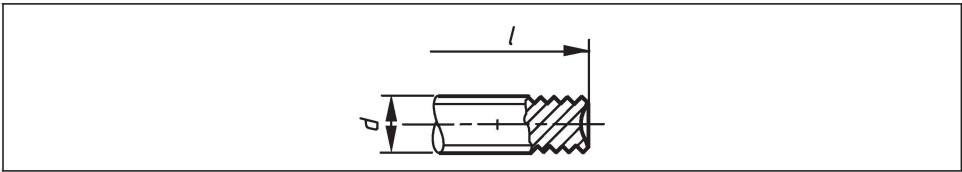

7 Screw threads

7.1 General

The form of thread, and diameters and associated pitches of standard ISO metric bolts, screws and nuts shall be in accordance with BS 3643-1.

7.2 Tolerances

Unless otherwise agreed between the purchaser and the manufacturer (see 3.2), the tolerances on the screw threads shall be in accordance with BS 3643-2, as detailed below in Table 2.

Table 2 Thread tolerance classes

Product	Tolerance class
Bolts and screws	6g
Nuts (faced)	6H
Nuts (used with galvanized bolts)	6AZ (in accordance with BS ISO 965-5)

8 Length of thread on bolts and screws

8.1 Bolts

8.1.1 The length of thread on bolts shall be the distance from the end of the bolt (including any chamfer or radius) to the leading face of a screw ring gauge, which has been screwed as far as possible on to the bolt by hand.

8.1.2 The standard thread lengths, shall be in accordance with Table 3.

NOTE The values given in Table D.2 are based on the formulae given in Table 3.

Table 3 Basis for standard thread lengths

Nominal length of bolt <i>l</i>	Length of thread <i>b</i>
Up to and including 125 mm	$2d + 6 \text{ mm}$
Over 125 mm up to and including 200 mm	$2d + 12 \text{ mm}$
Over 200 mm	$2d + 25 \text{ mm}$

8.1.3 The length of thread runout shall not exceed the values given in column 3 of Table 4 (see Clause 4).

8.1.4 Bolts that are too short for minimum thread lengths shall be threaded as screws and shall be designated screws.

NOTE Further guidance on this is given in Annex D.

8.2 Tolerances

8.2.1 The tolerances on bolt thread lengths shall be plus two pitches for all diameters (see Table D.2).

8.2.2 The eccentricity of the thread relative to the shank of bolts shall not exceed the values given in Table 4b, column 19.

8.3 Screws

Screws shall be threaded to permit a screw ring gauge being screwed by hand to within a distance from the underside of the head not exceeding two and a half times the pitch for diameters up to and including 52 mm and three and a half times the pitch for diameters over 52 mm, in accordance with Table 4a, column 3.

9 Dimensions of bolts and screws

The dimensions of bolts and screws are in Table 4a and Table 4b. Figure 3, Figure 4 and Figure 5 give the explanation for those dimensions.

NOTE See Annex F for the recommended range of sizes for hexagon head bolts.

Figure 3 Hexagon head bolt, washer-faced

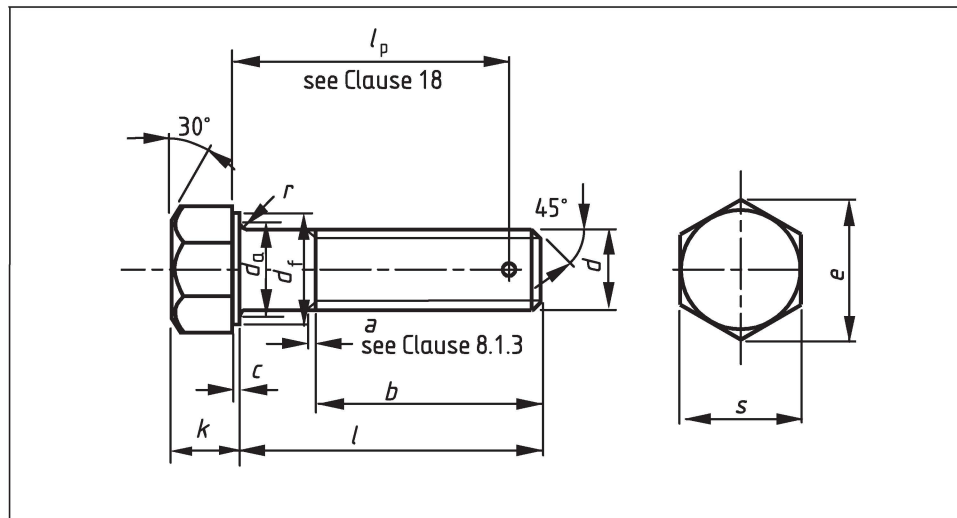


Figure 4 Hexagon head screw, washer-faced

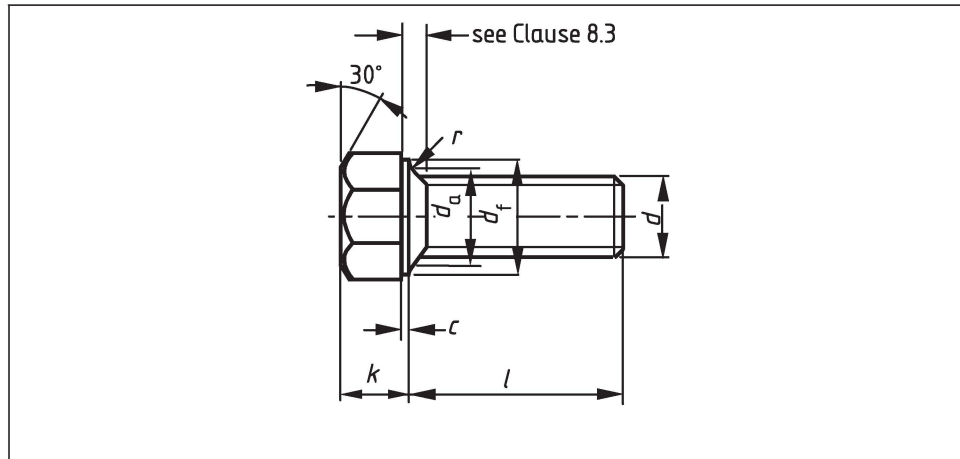


Figure 5 Full bearing head

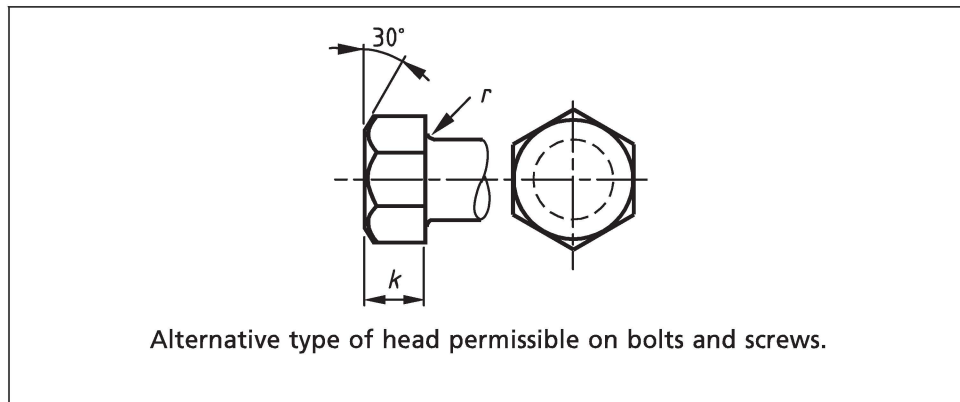


Table 4a ISO metric precision hexagon bolts and screws (1 of 2)

Dimensions in millimetres										
1	2	3	4	5	6	7	8	9	10	11
Nominal size and thread diameter <i>d</i>	Pitch of (thread series)	Thread runout <i>a</i> max.	Diameter of shank <i>d</i>		Width across flats <i>s</i>		Width across corners <i>e</i>		Diameter of washer face <i>d</i>	
			max.	min.	max.	min.	max.	min.	max.	min.
M1.6	0.35	0.8	1.6	1.46	3.2	3.08	3.7	3.48	—	—
M2	0.4	1.0	2.0	1.86	4.0	3.88	4.6	4.38	—	—
M2.5	0.45	1.0	2.5	2.23	5.0	4.88	5.8	5.51	—	—
M3	0.5	1.2	3.0	2.86	5.5	5.38	6.4	6.08	5.08	4.83
M4	0.7	1.6	4.0	3.82	7.0	6.85	8.1	7.74	6.55	6.30
M5	0.8	2.0	5.0	4.82	8.0	7.85	9.2	8.87	7.55	7.30
M6	1	2.5	6.0	5.82	10.0	9.78	11.5	11.05	9.48	9.23
M8	1.25	3.0	8.0	7.78	13.0	12.73	15.0	14.38	12.43	12.18
M10	1.5	3.5	10.0	9.78	17.0	16.73	19.6	18.9	16.43	16.18
M12	1.75	4.0	12.0	11.73	19.0	18.67	21.9	21.10	18.37	18.12
(M14)	2	5.0	14.0	13.73	22.0	21.67	25.4	24.49	21.37	21.12
M16	2	5.0	16.0	15.73	24.0	23.67	27.7	26.75	23.27	23.02
(M18)	2.5	6.0	18.0	17.73	27.0	26.67	31.2	30.14	26.27	26.02
M20	2.5	6.0	20.0	19.67	30.0	29.67	34.6	33.53	29.27	28.80
(M22)	2.5	6.0	22.0	21.67	32.0	31.61	36.9	35.72	31.21	30.74
M24	3	7.0	24.0	23.67	36.0	35.38	41.6	39.98	34.98	34.51
(M27)	3	7.0	27.0	26.67	41.0	40.38	47.3	45.63	39.98	39.36
M30	3.5	8.0	30.0	29.67	46.0	45.38	53.1	51.28	44.98	44.36
(M33)	3.5	8.0	33.0	32.61	50.0	49.38	57.7	55.80	48.98	48.36
M36	4	10.0	36.0	35.61	55.0	54.26	63.5	61.31	53.86	53.24
(M39)	4	10.0	39.0	38.61	60.0	59.26	69.3	66.96	58.86	58.24
M42	4.5	11.0	42.0	41.61	65.0	64.26	75.1	72.61	63.76	63.04
(M45)	4.5	11.0	45.0	44.61	70.0	69.26	80.8	78.26	68.76	68.04
M48	5	12.0	48.0	47.61	75.0	74.26	86.6	83.91	73.76	73.04
(M52)	5	12.0	52.0	51.54	80.0	79.26	92.4	89.56	—	—
M56	5.5	19.0	56.0	55.54	85.0	84.13	98.1	95.07	—	—
(M60)	5.5	19.0	60.0	59.54	90.0	89.13	103.9	100.72	—	—
M64	6	21.0	64.0	63.54	95.0	94.13	109.7	106.37	—	—

Table 4a ISO metric precision hexagon bolts and screws (2 of 2)

Dimensions in millimetres										
1	2	3	4	5	6	7	8	9	10	11
Nominal size and thread diameter <i>d</i>	Pitch of (thread series)	Thread runout <i>a</i> max.	Diameter of shank <i>d</i>		Width across flats <i>s</i>		Width across corners <i>e</i>		Diameter of washer face <i>d</i>	
			max.	min.	max.	min.	max.	min.	max.	min.
(M68)	6	21.0	68.0	67.54	100.0	99.13	115.5	112.02	—	—

NOTE Sizes shown in brackets are non-preferred.

Table 4b ISO metric precision hexagon bolts and screws (1 of 2)

Dimensions in millimetres								
11	12	13	14	15	16	17	18	19
Nominal size and thread diameter <i>d</i>	Depth of washer face <i>c</i>	Transition diameter <i>d_a</i> max.	Radius under head <i>r</i>		Height of head <i>k</i>		Eccentricity of head max.	Eccentricity of shank and split pin hole to the thread max.
			max.	min.	max.	min.		
M1.6	—	2.0	0.2	0.1	1.23	0.98	0.18	0.14
M2	—	2.6	0.3	0.1	1.53	1.28	0.18	0.14
M2.5	—	3.1	0.3	0.1	1.83	1.58	0.18	0.14
M3	0.1	3.6	0.3	0.1	2.13	1.90	0.18	0.14
M4	0.1	4.7	0.35	0.2	2.93	2.68	0.22	0.18
M5	0.2	5.7	0.35	0.2	3.66	3.35	0.22	0.18
M6	0.3	6.8	0.4	0.25	4.15	3.85	0.22	0.18
M8	0.4	9.2	0.6	0.4	5.65	5.35	0.27	0.22
M10	0.4	11.2	0.6	0.4	7.18	6.82	0.27	0.22
M12	0.4	14.2	1.1	0.6	8.18	7.82	0.33	0.27
(M14)	0.4	16.2	1.1	0.6	9.18	8.82	0.33	0.27
M16	0.4	18.2	1.1	0.6	10.18	9.82	0.33	0.27
(M18)	0.4	20.2	1.1	0.6	12.22	11.79	0.33	0.27
M20	0.4	22.4	1.2	0.8	13.22	12.79	0.33	0.33
(M22)	0.4	24.4	1.2	0.8	14.22	13.79	0.39	0.33

Table 4b ISO metric precision hexagon bolts and screws (2 of 2)

Dimensions in millimetres								
11	12	13	14	15	16	17	18	19
Nominal size and thread diameter <i>d</i>	Depth of washer face <i>c</i>	Transition diameter <i>d_a</i> max.	Radius under head <i>r</i>		Height of head <i>k</i>		Eccentricity of head max.	Eccentricity of shank and split pin hole to the thread max.
			max.	min.	max.	min.		
M24	0.5	26.4	1.2	0.8	15.22	14.79	0.39	0.33
(M27)	0.5	30.4	1.7	1.0	17.22	16.79	0.39	0.33
M30	0.5	33.4	1.7	1.0	19.26	18.74	0.39	0.33
(M33)	0.5	36.4	1.7	1.0	21.26	20.74	0.39	0.39
M36	0.5	39.4	1.7	1.0	23.26	22.74	0.46	0.39
(M39)	0.6	42.4	1.7	1.0	25.26	22.74	0.46	0.39
M42	0.6	45.6	1.8	1.2	26.26	25.74	0.46	0.39
(M45)	0.6	48.6	1.8	1.2	28.26	27.74	0.46	0.39
M48	0.6	52.6	2.3	1.6	30.26	29.74	0.46	0.39
(M52)	—	56.6	2.3	1.6	33.21	32.69	0.46	0.46
M56	—	63.0	3.5	2.0	35.31	34.69	0.54	0.46
(M60)	—	67.0	3.5	2.0	38.31	37.69	0.54	0.46
M64	—	71.0	3.5	2.0	40.31	39.69	0.54	0.46
(M68)	—	75.0	3.5	2.0	43.31	42.69	0.54	0.46

^{A)} A true radius is not essential providing that the curve is smooth and lies wholly within the maximum radius, determined from the maximum transitional diameter and the minimum radius specified.

10 Angularity and eccentricity of bolts, screws and nuts

10.1 The axis of the thread of the nut shall be square to the face of the nut subject to the "squareness tolerance" given in column 9 of Table 5, which is equivalent to an out of squareness of $\pm 1^\circ$.

10.2 The nut shall be screwed by hand on to a gauge having a truncated taper thread until the thread of the nut is tight on the thread of the gauge. A sleeve sliding on a parallel extension of the gauge, and which has a face of diameter equal to the minimum distance across flats of the nut, and at exactly 90° to the axis of the gauge, shall be brought into contact with the leading face of the nut.

10.3 The sleeve shall be in such a position so that it is not possible for a feeler gauge of thickness equal to the squareness tolerance to enter anywhere between the leading face of the nut and face of the sleeve (see Annex B).

10.4 The hexagon flats of bolts, screws and nuts shall be square to the bearing face, and the angularity of the head shall be within the limits of $90^\circ \pm 1^\circ$ (see Annex E).

10.5 The eccentricity of the hexagon flats of nuts relative to the thread diameter shall not exceed the values given in Table 5, column 10.

10.6 The eccentricity of the head relative to the width across flats and eccentricity between the shank and thread of bolts and screws shall not exceed the values given in column 18 and 19, respectively, of Table 4b.

11 Dimensions of nuts

Figure 6 to Figure 8 show the symbols used in Table 5 for nut dimensions. Figure 9 to Figure 11 show the symbols used in Table 6.

Figure 6 Normal thickness nut

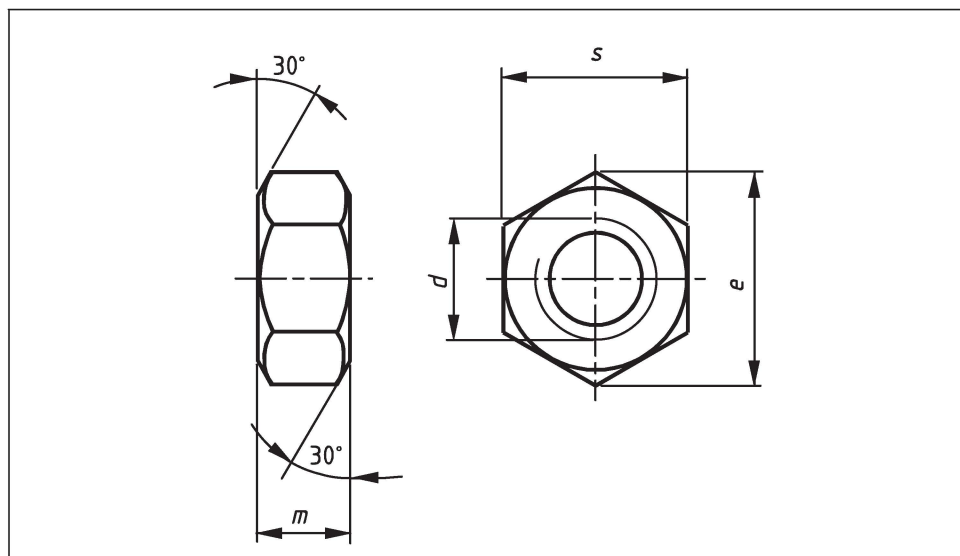


Figure 7 Thin nut

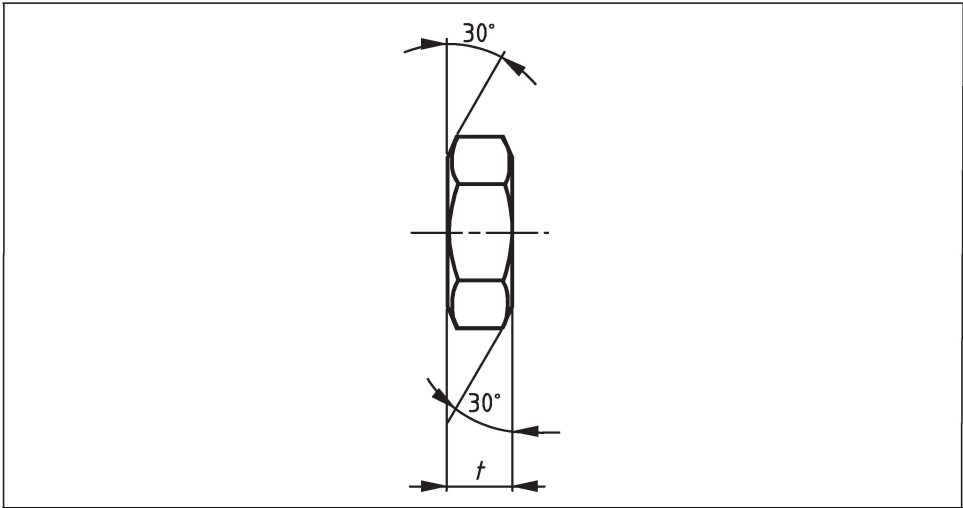


Figure 8 Enlarged view of nut countersunk

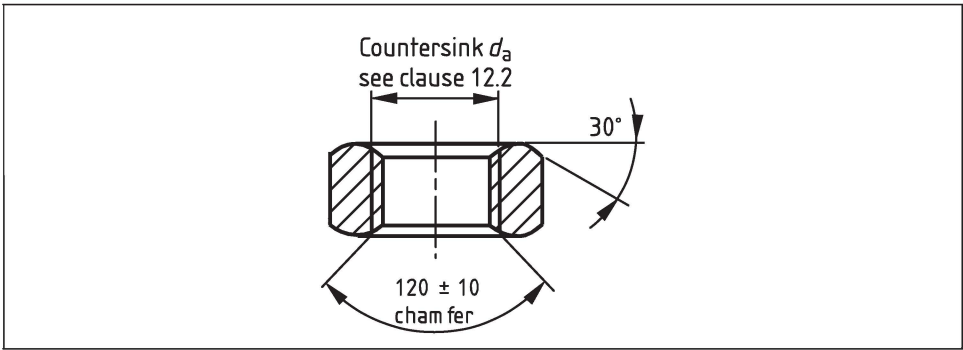


Table 5 ISO metric precision hexagon nuts and thin nuts (1 of 2)

Dimensions in millimetres											
1	2	3	4	5	6	7	8	9	10	11	12
Nominal size and thread diameter <i>d</i>	Pitch of thread (coarse pitch series)	Width across flats		Width across corners		Thickness of normal nut		Tolerance on squareness of thread to face of nut	Eccentricity of hexagon	Thickness of thin nut	
		<i>s</i>		<i>e</i>		<i>m</i>				<i>t</i>	
		max.	min.	max.	min.	max.	min.	max.	max.	max.	min
M1.6	0.35	3.20	3.08	3.70	3.48	1.30	1.05	0.05	0.14	—	—
M2	0.4	4.00	3.88	4.60	4.38	1.60	1.35	0.06	0.14	—	—
M.2	0.45	5.00	4.88	5.80	5.51	2.00	1.75	0.08	0.14	—	—
M3	0.5	5.50	5.38	6.40	6.08	2.40	2.15	0.09	0.14	—	—
M4	0.7	7.00	6.85	8.10	7.74	3.20	2.90	0.11	0.18	—	—
M5	0.8	8.00	7.85	9.20	8.87	4.00	3.70	0.13	0.18	—	—
M6	1	10.00	9.78	11.50	11.05	5.00	4.70	0.17	0.18	—	—
M8	1.25	13.00	12.73	15.00	14.38	6.50	6.14	0.22	0.22	5.0	4.70
M10	1.50	17.00	16.73	19.60	18.90	8.00	7.64	0.29	0.22	6.0	5.70
M12	1.75	19.00	18.67	21.90	21.10	10.00	9.64	0.32	0.27	7.0	6.64
(M14)	2	22.00	21.67	25.40	24.49	11.00	10.57	0.37	0.27	8.0	7.64
M16	2	24.00	23.67	27.70	26.75	13.00	12.57	0.41	0.27	8.0	7.64
(M18)	2.5	27.00	26.67	31.20	30.14	15.00	14.57	0.46	0.27	9.0	8.64
M20	2.5	30.00	29.67	34.60	33.53	16.00	15.57	0.51	0.33	9.0	8.64
(M22)	2.5	32.00	31.67	36.90	35.72	18.00	17.57	0.54	0.33	10.0	9.64
M24	3	36.00	35.38	41.60	39.98	19.00	18.48	0.61	0.33	10.0	9.64
(M27)	3	41.00	40.38	47.30	45.63	22.00	21.48	0.70	0.33	12.0	11.57
M30	3.5	46.00	45.38	53.10	51.28	24.00	23.48	0.78	0.33	12.0	11.57
(M33)	3.5	50.00	49.38	57.70	55.80	26.00	25.48	0.85	0.39	14.0	13.57
M36	4	55.00	54.26	63.50	61.31	29.00	28.48	0.94	0.39	14.0	13.57
(M39)	4	60.00	59.26	69.30	66.96	31.00	30.38	1.03	0.39	16.0	15.57
M42	4.5	65.00	64.26	75.10	72.61	34.00	33.38	1.11	0.39	16.0	15.57
(M45)	4.5	70.00	69.26	80.80	78.26	36.00	35.38	1.20	0.39	18.0	17.57
M48	5	75.00	74.26	86.60	83.91	38.00	37.38	1.29	0.39	18.0	17.57
(M52)	5	80.00	79.26	92.40	89.56	42.00	41.38	1.37	0.46	20.0	19.48

Table 5 ISO metric precision hexagon nuts and thin nuts (2 of 2)

Dimensions in millimetres											
1	2	3	4	5	6	7	8	9	10	11	12
Nominal size and thread diameter <i>d</i>	Pitch of thread (coarse pitch series)	Width across flats		Width across corners		Thickness of normal nut		Tolerance on squareness of thread to face of nut	Eccentricity of hexagon	Thickness of thin nut	
		<i>s</i>		<i>e</i>		<i>m</i>				<i>t</i>	
		max.	min.	max.	min.	max.	min.	max.	max.	max.	min
M56	5.5	85.00	84.13	98.10	95.07	45.00	44.38	1.46	0.46	—	—
(M60)	5.5	90.00	89.13	103.90	100.72	48.00	47.38	1.55	0.46	—	—
M64	6	95.00	94.13	109.70	106.37	51.00	50.26	1.63	0.46	—	—

NOTE 1 Sizes shown in brackets are non-preferred.

NOTE 2 For tolerances on squareness of thread to face of nut, see Annex B.

Figure 9 Slotted nut. Sizes M4 to M39 only (six slots)

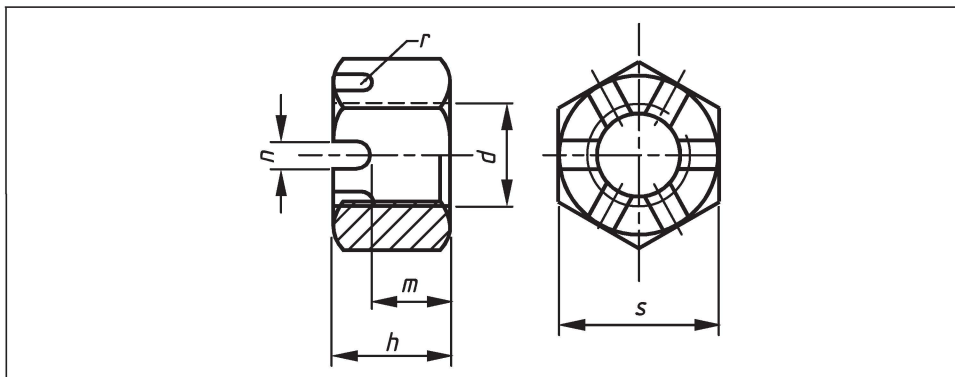


Figure 10 Castle nut. Sizes M12 to M39 only (six slots)

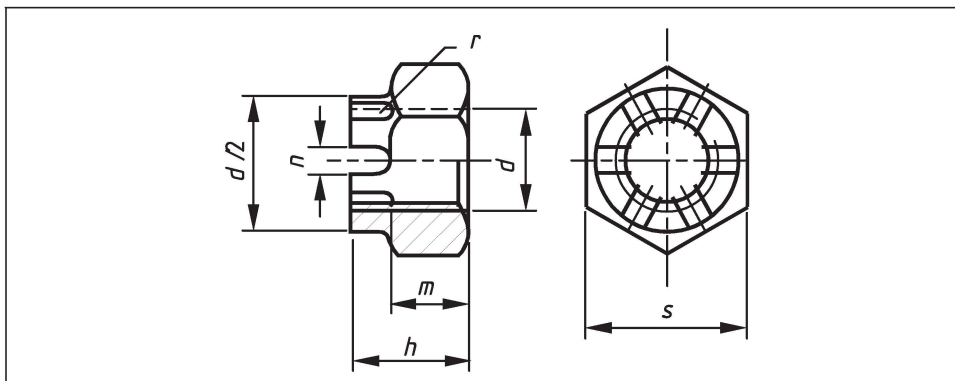


Figure 11 Castle nut. Sizes M42 to M68 only (eight slots)

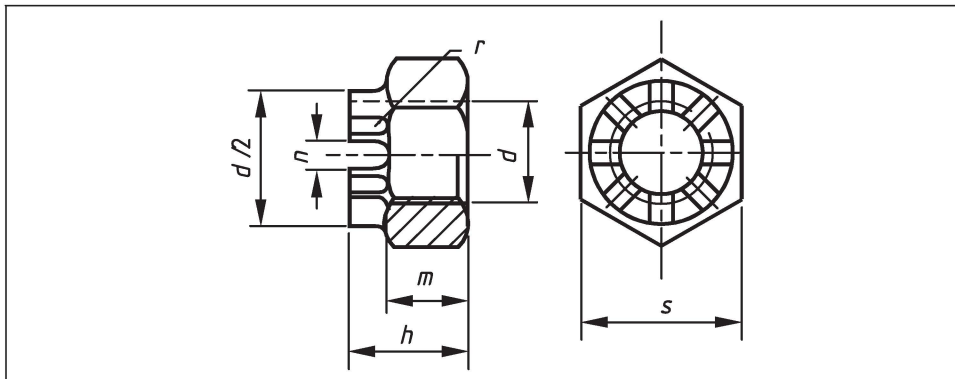


Table 6 – ISO metric precision hexagon slotted nuts and castle nuts

Dimensions in millimetres										Nominal size of split pin and nominal drill	Eccentricity of the slots max.
Nominal size and thread diameter <i>d</i>	Diameter <i>d</i> ₂		Thickness <i>h</i>		Lower face of nut to bottom of slot <i>m</i>		Width of slot <i>n</i>		Radius (0.25 <i>n</i>) <i>r</i>		
	max.	min.	max.	min.	max.	min.	max.	min.	min.		
M4	—	—	5	4.70	3.2	2.90	1.45	1.2	0.3	It is intended to provide appropriate values in this column once International agreement has been reached on metric series split cotter pins	0.18
M5	—	—	6	5.70	4	3.70	1.65	1.4	0.35		0.18
M6	—	—	7.5	7.14	5	4.70	2.25	2	0.5		0.18
M8	—	—	9.5	9.14	6.5	6.14	2.75	2.5	0.625		0.22
M10	—	—	12	11.57	8	7.64	3.05	2.8	0.7		0.22
M12	17	16.57	15	14.57	10	9.64	3.80	3.5	0.875		0.27
(M14)	19	18.48	16	15.57	11	10.57	3.80	3.5	0.875		0.27
M16	22	21.48	19	18.48	13	12.57	4.80	4.5	1.125		0.27
(M18)	25	24.48	21	20.48	15	14.57	4.80	4.5	1.125		0.27
M20	28	27.48	22	21.48	16	15.57	4.80	4.5	1.125		0.33
(M22)	30	29.48	26	25.48	18	17.57	5.80	5.5	1.375		0.33
M24	34	33.38	27	26.48	19	18.48	5.80	5.5	1.375		0.33
(M27)	38	37.38	30	29.48	22	21.48	5.80	5.5	1.375		0.33
M30	42	41.38	33	32.38	24	23.48	7.36	7	1.75		0.33
(M33)	46	45.38	35	34.38	26	25.48	7.36	7	1.75		0.39
M36	50	49.38	38	37.38	29	28.48	7.36	7	1.75		0.39
(M39)	55	54.26	40	39.38	31	30.38	7.36	7	1.75		0.39
M42	58	57.26	46	45.38	34	33.38	9.36	9	2.25		0.39
(M45)	62	61.26	48	47.38	36	35.38	9.36	9	2.25		0.39
M48	65	64.26	50	49.38	38	37.38	9.36	9	2.25		0.39
(M52)	70	69.26	54	53.26	42	41.38	9.36	9	2.25		0.46
M56	75	74.26	57	56.26	45	44.38	9.36	9	2.25		0.46
(M60)	80	79.26	63	62.26	48	47.38	11.43	11	2.75		0.46
M64	85	84.13	66	65.26	51	50.26	11.43	11	2.75		0.46
M68	90	89.13	69	68.26	54	53.26	11.43	11	2.75		0.46

NOTE 1 For width across flats and widths across corners, see Table 5.

NOTE 2 Sizes shown in brackets are non-preferred.

12 Chamfering, washer facing and countersinking bolts, screws and nuts

12.1 Bolts and screws

Bolt and screw heads shall have a chamfer of approximately 30° on their upper faces and, at the option of the manufacturer, a washer face or full bearing face on the underside unless the purchaser in their enquiry or order specifically states that they require one of the alternatives available.

NOTE Attention is drawn to the fact that these alternative methods of finishing the underside of bolt and screw heads are associated with both the nominal size and the particular method of manufacture. A request by the purchaser for a specific type of finish limits the manufacturing processes available.

12.2 Nuts

12.2.1 Nuts shall have a chamfer of approximately 30° on both faces in accordance with Figure 8.

12.2.2 Nuts shall be countersunk at an included angle of 120° ±10° at both ends of the thread. The diameter of the countersink shall conform to the requirement of BS EN ISO 4759-1:2001, Figure 69 as follows:

$$d \leq 5 \text{ mm: } d_{a \text{ max}} = 1.15d$$

$$5 \text{ mm} < d \leq 8 \text{ mm: } d_{a \text{ max}} = d + 0.75$$

$$d > 8 \text{ mm: } d_{a \text{ max}} = 1.08d$$

$$\text{for all sizes: } d_{a \text{ min}} = d$$

NOTE Requirements are applicable to both sides of symmetrical parts.

13 Material and manufacture of steel bolts and screws

13.1 Method of production

At the discretion of the manufacturer, steel bolts and screws shall, be produced by cold forging, hot forging or by turning from bar.

13.2 Chemical composition

COMMENTARY ON 13.2

The chemical compositions of steels with respect to carbon, phosphorus, sulfur and boron is given in BS EN ISO 898-1:2013¹⁾, Table 2, and the chemical compositions of steels given are for guidance only. The choice of steels, which conform to these specified limits, is at the discretion of the manufacturer.

The steel used shall be such that the finished product possesses the mechanical properties appropriate to the strength grade quoted.

13.3 Heat treatment

Grades designated 8.8, 10.9, and 12.9 shall be heat-treated to give the mechanical properties given in BS EN ISO 898-1.

¹⁾ BS EN ISO 898-1:2013, *Mechanical properties of fasteners made of carbon steel and alloy steel.*

NOTE Other grades may be heat-treated if this is necessary to obtain the mechanical properties given in BS EN ISO 898-1.


13.4 Decarburization

13.4.1 Decarburization of the thread surface shall not be greater than stipulated in 13.4.2 and 13.4.3 for bolts and screws of grade designations 8.8, 10.9, and 12.9.

13.4.2 The depth of the non-decarburized zone shall be not less than two thirds of the depth of the basic thread. In the root of the thread, the decarburization shall not exceed one tenth of the depth of the basic thread (see Figure 12).

13.4.3 The method of measuring the amount of decarburization shall be as specified in BS EN ISO 898-1.

Figure 12 Depth of decarburization on steel bolts and screws

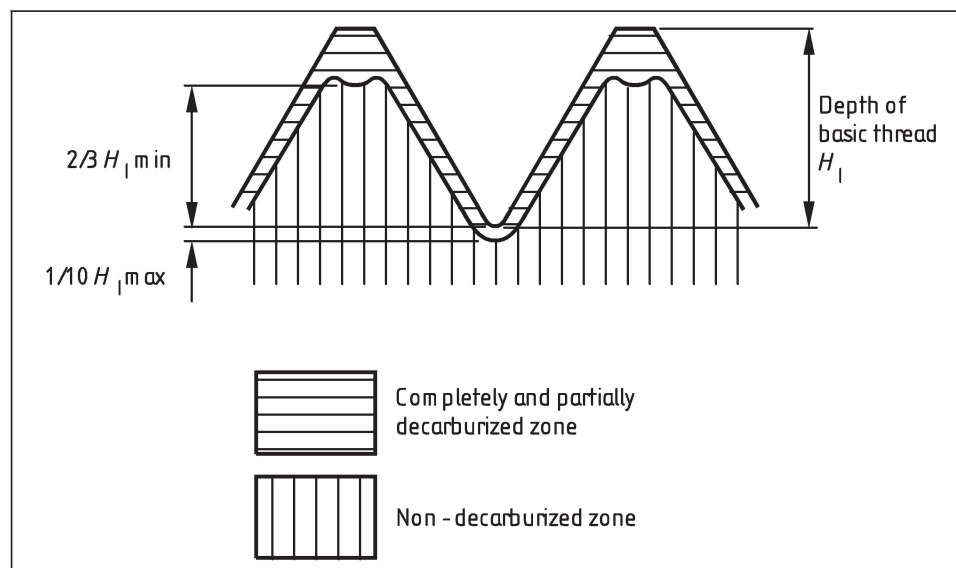

13.5 Rolling laps

COMMENTARY ON 13.5

When threads are produced by rolling, small laps are commonly present at the crests and are generally of a magnitude which is not detrimental to the performance of the bolt.

13.5.1 A lap formed at the crest of the thread perpendicular to the axis of the bolt shall not be a cause for rejection if the depth of the lap does not exceed 33% of the depth of the thread.

13.5.2 Bolts of grades designated 10.9 and 12.9 shall be free from laps in the thread flank below the effective diameter. Laps in the flanks above the effective diameter shall not have a depth greater than 33% of the thread depth.

14 Mechanical properties of steel bolts and screws

Steel bolts and screws shall meet the requirements for mechanical properties given in BS EN ISO 898-1.

NOTE The strength grade designation system for bolts and screws is given in Annex A.

15 Strength grade designation system for steel nuts

The strength grade designation system for steel nuts shall be a number that is one hundredth of the specified proof load stress in MPa.

NOTE 1 The proof load stress corresponds to one hundredth of the nominal tensile strength of the highest grade of bolt, stud or screw with which the nut can be used (see Table 7).

NOTE 2 The mechanical properties of steel nuts are given in Clause 17. It is recommended that the grades of nut to be used with each grade of bolt or screw should be as shown in Table 8.

Table 7 Strength grade designation of steel nuts

Strength grade designation	4	5	6	8	10	12
Proof load stress MPa	400	500	600	800	1 000	1 200

Table 8 Recommended bolt and nut combinations

Grade of bolt	4.6	4.8	5.6	5.8	6.8	8.8	8.8 ^{A)}	10.9	10.9 ^{A)}	12.9
Recommended grade of nut	4	4	5	5	6	8	10	10	12	12

^{A)} When a thick protective coating is applied to a bolt of grade 8.8 or 10.9 which requires the nut thread to be overtapped, the next higher grade of nut should be used.

NOTE 1 The nuts in Table 7 are at least 15% lower in height than ISO metric 'Regular' nuts, in BS EN ISO 4032 for example. Therefore they are not capable of withstanding the same tensile loads without the risk of thread stripping (see also Foreword).

NOTE 2 Nuts of a higher strength grade may be substituted for nuts of a lower strength grade.

16 Material and manufacture of steel nuts

16.1 Method of manufacture

Steel nuts shall be produced by cold forging, hot forging or by turning from bar. The choice of manufacture is at the option of the manufacturer.

16.2 Chemical composition

The chemical composition of materials from which steel nuts shall be made are given in Table 9.

NOTE The use of free-cutting steels at temperatures above 250°C is not recommended. Free-cutting steel may be used where permitted in Table 9, or otherwise by special agreement between the purchaser and the supplier.

Table 9 Chemical composition of steel nuts

Strength grade designation	Chemical composition limits (check analysis)			
	Carbon max. %	Manganese min. %	Phosphorus max. %	Sulfur max. %
4, 5 and 6 (See notes)	0.50	—	0.110	0.150
8	0.58	0.30	0.060	0.150
10 and 12 (See notes)	0.58	0.45	0.048	0.058

NOTE 1 Free cutting steel may be used only by special agreement between the purchaser and the supplier. In such cases, the following maximum phosphorus, sulfur and lead contents are permissible:

Phosphorus, 0.12%; Sulfur, 0.34%; Lead, 0.35%.

NOTE 2 Alloying elements may be added if necessary to develop the mechanical properties of the nuts stipulated in Clause 17.

16.3 Heat treatment

Nuts shall be heat-treated where this is necessary to obtain the mechanical properties given in Clause 17.

17 Mechanical properties of steel nuts (excluding thin nuts)

Steel nuts (excluding thin nuts) shall meet the requirements for mechanical properties given in Table 10. The nuts shall withstand the proof load stress given in Table 10 when tested in accordance with Annex C. Nuts that are proof load tested shall have a hardness not in excess of the maximum given in Table 10. Nuts which are not proof load tested shall have a hardness not less than the minimum agreed between the purchase and the supplier and not more than the maximum given in Table 10. The tests shall be in accordance with Annex C.

Table 10 Mechanical properties of steel nuts

Strength grade designation	4	5	6	8	10	12	
Proof load stress ^{A)} MPa	400	500	600	800	1 000	1 200	— ^{C)}
Brinell hardness (HB) max.	302	302	302	302	353	375	All nuts
Rockwell hardness ^{B)} (HRC) max.	30	30	30	30	36	39	All nuts
Vickers hardness (HV) max.	310	310	310	310	370	395	All nuts

NOTE For materials and mechanical properties of hexagon bolts and screws, refer to BS EN ISO 898-1.

^{A)} The proof load is calculated by multiplying the proof load stress by the tensile stress area of the bolt.

^{B)} The conversion from Brinell hardness into Rockwell hardness has been calculated in accordance with BS EN ISO 6506-1 BS EN ISO 6506-2 and BS EN ISO 6506-3, and BS EN ISO 6508-1.

^{C)} All nuts other than those exempted by agreement between the purchaser and the manufacturer. Nuts with a specified proof load in excess of 500 000 N (see Table 11) may be except from proof load testing. Such nuts shall meet the minimum hardness as agreed between the purchaser and the manufacturer.

Table 11 Proof loads for steel nuts (coarse pitch series) (1 of 2)

Nominal size of nut mm	Tensile stress area of bolt mm²	Strength grade designation					
		4	5	6	8	10	12
		Stress under proof load					
		MPa					
		400	500	600	800	1 000	1 200
Proof load							
N							
M1.6	1.27	510	640	760	1 020	1 270	1 520
M2	2.07	830	1 030	1 240	1 650	2 070	2 480
M2.5	3.39	1 360	1 700	2 030	2 710	3 390	4 070
M3	5.03	2 010	2 520	3 020	4 000	5 000	6 000
M4	8.78	3 510	4 400	5 250	7 000	8 750	10 500
M5	14.2	5 680	7 100	8 500	11 400	14 200	17 000
M6	20.1	8 040	10 000	12 000	16 000	20 000	24 000
M8	36.6	14 600	18 300	22 000	29 000	36 500	43 000
M10	58.0	23 200	29 000	35 000	46 000	58 000	69 500
M12	84.3	33 700	42 100	50 500	67 000	84 000	100 000
M14	115	46 000	57 500	69 000	92 000	115 000	138 000
M16	157	62 800	78 500	94 000	125 000	157 000	188 000
M18	192	76 800	98 000	115 000	154 000	192 000	230 000
M20	245	98 000	122 000	147 000	196 000	245 000	294 000
M22	303	121 000	151 000	182 000	242 000	303 000	364 000
M24	353	141 000	175 000	212 000	282 000	353 000	423 000
M27	459	184 000	230 000	276 000	367 000	459 000	550 000
M30	561	224 000	280 000	336 000	448 000	561 000	673 000
M33	694	278 000	347 000	416 000	555 000	694 000	833 000
M36	817	327 000	408 000	490 000	653 000	817 000	980 000
M39	976	390 000	488 000	585 000	780 000	976 000	1 170 000
M42	1 120	448 000	560 000	672 000	896 000	1 120 000	1 340 000
M45	1 300	520 000	650 000	780 000	1 040 000	1 300 000	1 560 000
M48	1 470	588 000	735 000	882 000	1 180 000	1 470 000	1 760 000
M52	1 760	704 000	880 000	1 060 000	1 410 000	1 760 000	2 110 000

Table 11 Proof loads for steel nuts (coarse pitch series) (2 of 2)

Nominal size of nut mm	Tensile stress area of bolt mm²	Strength grade designation					
		4	5	6	8	10	12
		Stress under proof load					
		MPa					
		400	500	600	800	1 000	1 200
		Proof load					
		N					
M56	2 030	812 000	1 015 000	1 220 000	1 620 000	2 030 000	2 440 000
M60	2 360	944 000	1 180 000	1 420 000	1 890 000	2 360 000	2 830 000
M64	2 680	1 072 000	1 340 000	1 610 000	2 140 000	2 680 000	3 220 000
M68	3 060	1 224 000	1 530 000	1 840 000	2 450 000	3 060 000	3 670 000

NOTE 1 Proof load = Stress under proof × tensile stress area of bolt

NOTE 2 For stress under proof load, see Table 10.

NOTE 3 Nuts with a specified proof load above 500 000 N force may be exempted from proof load testing, see Clause 17 and Table 10.

18 Drilled bolts with split pin holes

18.1 Bolts with split pin holes are supplied only when specially ordered. The purchaser usually states, in the enquiry and order, dimension l_p , as illustrated in Figure 3.

18.2 A tolerance of $-0 / +0.8$ mm shall be permissible on the specified dimension l_p .

18.3 The split pin holes shall be drilled through the centre of the bolt as specified in BS EN ISO 1234.

19 Finishes

Steel precision bolts, screws and nuts shall be supplied with one of finishes given in Table 12.

Table 12 Finishes

Product type	Finishes
Heat-treated bolts and screws	Components heat-treated after manufacture shall be dull black, although the manufacturer might machine some of the surfaces of the larger size bolts and screws after heat treatment.
Bright finished bolts and screws	This term is used to describe bolts and screws which are finished bright on all surfaces or which have a finish on the hexagon, produced by bright drawing.
Nuts	These can be bright on all surfaces or dull black when heat-treated.
Other finishes	If the purchaser requires bolts, screws or nuts (or other material) to be coated, the type of coating required should be stated in their enquiry and order, where reference should be made to the appropriate British Standard, i.e. BS EN ISO 4042, BS 7371-6 or BS EN ISO 10684.

NOTE If steel bolts, screws or nuts are required finished bright all over, this is usually stated in the enquiry and order.

20 Marking and identification

COMMENTARY ON CLAUSE 20

The marking and identification requirements of this British Standard are applicable to steel bolts, screws and nuts of 6 mm diameter and larger; manufactured to strength grade designations 8.8 (for bolts or screws) and 8 (for nuts) or higher.

20.1 Bolts and screws

Marking of bolts and screws shall be in accordance with BS EN ISO 898-1:2013, Clause 10.

20.2 Nuts

Nuts shall be marked with the strength grade designation between two vertical bars as shown in Table 13.

Table 13 **Marking of nuts**

Strength grade designation	8	10	12
Marking symbol	8	10	12

21 Inspection and testing

Tests for mechanical properties shall be in accordance with BS EN ISO 898-1 for bolts and screws and Annex C for nuts.

Annex A
(informative)

Strength grade designation system for steel bolts and screws

Being in accordance with BS EN ISO 898-1, the strength grade designation system (property class symbol) for steel bolts and screws consists of two numbers separated by a dot (see Table A.1). The number to the left of the dot is one hundredth of the nominal tensile strength in MPa, and the number to the right is 10 times the ratio between the nominal yield strength (or nominal stress at permanent set limit, R0.2 nom) and the nominal tensile strength.

Table A.1 — Strength grade designations of steel bolts and screws

Strength grade designation	4.6	4.8	5.6	5.8	6.8	8.8	10.9	12.9
Tensile strength Rm nominal. MPa	400	400	500	500	600	800	1 000	1 200
Yield stress Re nominal. MPa	240	320	300	400	480	—	—	—
Stress at permanent set limit R0.2 MPa	—	—	—	—	—	640	900	1 080


NOTE Refer to BS EN ISO 898-1 for full details of the range of mechanical property requirements for these strength grades.

Annex B
(informative)

Recommended gauge for checking squareness of thread to face of nut

Figure B.1 shows the recommended gauge for checking the squareness of the thread to the face of the nut.

Figure B.1 Nut squareness gauge

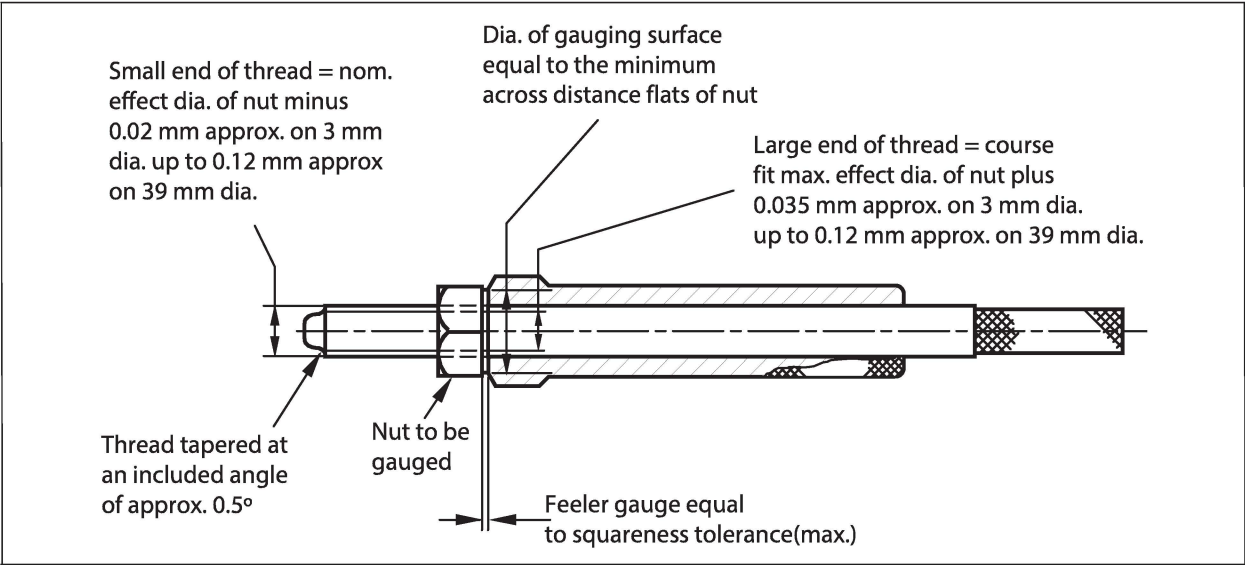

Annex C
(normative)
C.1


Testing of mechanical properties of steel nuts

Proof load test

C.1.1 The proof load test consists of applying the relevant proof load given in Table 11 which was obtained from the proof load stress given in Table 10.

C.1.2 Assemble the nut to be tested on a hardened and tempered mandrel as shown in Figure C.1 and apply the specified load in an axial direction.

Figure C.1 Proof load test for nut

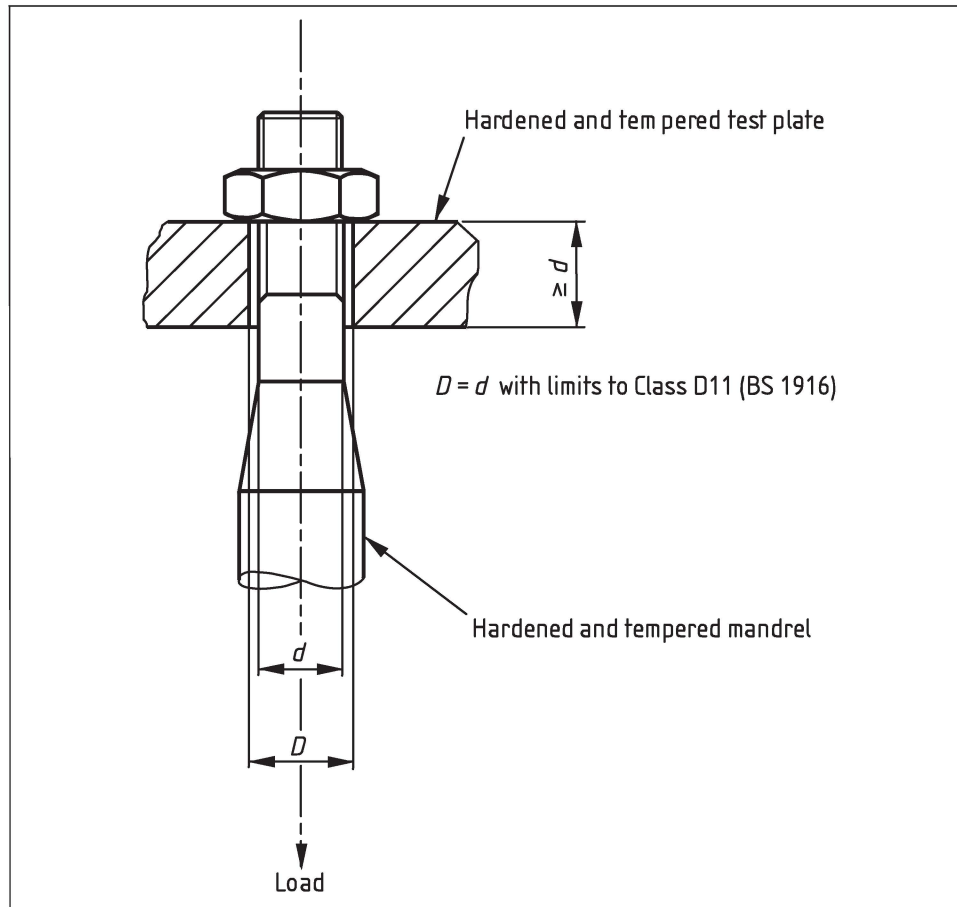

C.1.3 The nut shall withstand this load without failure by stripping or rupture, and shall be removable by hand after the load is released. If the threads of the mandrel are damaged during the test, the test shall be discarded.

NOTE It might be necessary to use a manual wrench to start the nut in motion. Such wrenching is permissible providing it is restricted to a half turn and the nut is then removable by hand after this initial loosening.

C.2 Hardened mandrel

The mandrel shall have a hardness of not less than Rockwell C45. The thread shall be tolerance class 5h except that the tolerance on the major diameter shall be the last quarter of the 6g range of the minimum material side.

C.3 Hardened test plate

The test plate shall have a hardness of not less than Rockwell C38.

C.4 Hardness test on nuts

C.4.1 Brinell, Rockwell and Vickers hardness may be determined. Apply the impression to the top and bottom face of the nut, otherwise on the side of the nut.

C.4.2 Perform a Brinell hardness test in accordance with BS EN ISO 6506-1, BS EN ISO 6506-2, BS EN ISO 6506-3 and BS EN ISO 6506-4.

C.4.3 Perform a Rockwell hardness test in accordance with BS EN ISO 6508-1, BS EN ISO 6508-2 and BS EN ISO 6508-3.

C.4.4 Perform a Vickers hardness test in accordance with of BS EN ISO 6507-1, BS EN ISO 6507-2, BS EN ISO 6507-3 and BS EN ISO 6507-4.

Annex D (informative)

Association of bolt and screw lengths and diameters (see Clause 8)

D.1 Table D.1a and Table D.1b give the preferred standard size of ISO metric precision hexagon bolts and screws.

Table D.1a Preferred standard sizes of ISO metric precision hexagon bolts and screws (1 of 2)

Nominal size and thread diameter <i>d</i>	Standard nominal lengths <i>l</i>																	Dimensions in millimetres									
	5	6	(7)	8	(9)	10	(11)	12	14	16	(18)	20	(22)	25	(28)	30	(32)	35	(38)	40	45	50	55	60	65	70	75
M1.6	X	X	O	X	O	X	O	X	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
M2	X	X	O	X	O	X	O	X	X	X	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
M2.5	X	X	O	X	O	X	O	X	X	X	O	X	O	X	—	—	—	—	—	—	—	—	—	—	—	—	—
M3	X	X	O	X	O	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	—	—	—	—	—
M4	X	X	O	X	O	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	—	X	X	X	—
M5	—	X	O	X	O	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M6	—	X	O	X	O	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M8	—	—	—	X	O	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M10	—	—	—	X	O	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M12	—	—	—	—	—	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
(M14)	—	—	—	—	—	X	O	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M16	—	—	—	—	—	—	—	X	X	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
(M18)	—	—	—	—	—	—	—	—	—	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M20	—	—	—	—	—	—	—	—	—	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
(M22)	—	—	—	—	—	—	—	—	—	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M24	—	—	—	—	—	—	—	—	—	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
(M27)	—	—	—	—	—	—	—	—	—	X	O	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X
M30	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	O	X	X	X	X	X	X	X	X
(M33)	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	O	X	X	X	X	X	X	X	X
M36	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	O	X	X	X	X	X	X	X	X
(M39)	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	O	X	X	X	X	X	X	X	X
M42	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	X	X	X	X	X	X	X
(M45)	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	X	X	X	X	X	X	X
M48	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	X	X	X	X	X	X	X
(M52)	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	X	X	X	X	X	X
M56	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
(M60)	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
M64	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—
(M68)	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—

Table D.1a Preferred standard sizes of ISO metric precision hexagon bolts and screws (2 of 2)

Nominal size and thread diameter <i>d</i>	Standard nominal lengths <i>l</i>																										Dimensions in millimetres									
	5	6	(7)	8	(9)	10	(11)	12	14	16	(18)	20	(22)	25	(28)	30	(32)	35	(38)	40	45	50	55	60	65	70	75									

- NOTE 1 *Bolded symbols screws only.*
- NOTE 2 *Sizes and lengths shown in brackets are non-preferred.*
- NOTE 3 *“x” indicates first choice length.*

Table D.1b Preferred standard sizes of ISO metric precision hexagon bolts and screws (1 of 2)

Nominal size and thread diameter <i>d</i>	Standard nominal lengths, <i>l</i>																											
	80	85	90	(95)	100	(105)	110	(115)	120	(125)	130	140	150	160	170	180	190	200	220	240	260	280	300	325	350	375	400	
M1.6	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M2	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M2.5	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M3	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M4	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M5	X	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M6	X	X	X	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M8	X	X	X	O	X	O	X	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	—	
M10	X	X	X	O	X	O	X	O	X	O	X	X	X	X	—	—	—	—	—	—	—	—	—	—	—	—	—	
M12	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	—	—	—	—	—	—	—	—	—	—	—	
(M14)	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	—	—	—	—	—	—	—	—	—	
M16	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	—	—	—	—	—	—	—	—	
(M18)	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	—	—	—	—	—	—	—	—	
M20	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	—	—	—	—	—	—	—	—	
(M22)	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	—	—	—	—	—	—	—	—	
M24	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	—	—	—	—	—	—	—	—	
(M27)	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
M30	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
(M33)	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
M36	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
(M39)	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
M42	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
M45	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
M48	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
(M52)	X	X	X	O	X	O	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
M56	—	—	—	—	—	—	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
(M60)	—	—	—	—	—	—	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
M64	—	—	—	—	—	—	X	O	X	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	
(M68)	—	—	—	—	—	—	—	—	—	O	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	X	

Table D.1b Preferred standard sizes of ISO metric precision hexagon bolts and screws (2 of 2)

Nomi- nal size and thread dia- meter <i>d</i>	Standard nominal lengths, <i>l</i>																											
	80	85	90	(95)	100	(105)	110	(115)	120	(125)	130	140	150	160	170	180	190	200	220	240	260	280	300	325	350	375	400	

- NOTE 1 *Bolded symbols screws only*
- NOTE 2 *Sizes and lengths shown in brackets are non-preferred.*
- NOTE 3 *"x" indicates first choice length.*

D.2 Table D.2 gives standard thread lengths and the shortest lengths designated as bolts, related to diameter.

Table D.2 **Standard thread lengths and the shortest lengths designated as bolts, related to diameter**

Nominal size and bolt diameter	Length of thread b for nominal bolt length /			Dimensions in millimetres	
	Up to 125 mm	Over 125 mm and up to 200 mm	Above 200 mm	Tolerance on bolt thread length	Shortest length designated as a bolt
<i>d</i>				<i>b</i>	
M1.6	9	—	—	+0.7	(11)
M2	10	—	—	+0.8	12
M2.5	11	—	—	+0.9	14
M3	12	—	—	+1.0	14
M4	14	—	—	+1.4	18
M5	16	—	—	+1.6	20
M6	18	—	—	+2.0	(22)
M8	22	—	—	+2.5	(28)
M10	26	32	—	+3.0	(32)
M12	30	36	—	+3.5	(38)
(M14)	34	40	—	+4.0	45
M16	38	44	57	+4.0	45
(M18)	42	48	61	+5.0	50
M20	46	52	65	+5.0	55
(M22)	50	56	69	+5.0	60
M24	54	60	73	+6.0	65
(M27)	60	66	79	+6.0	70
M30	66	72	85	+7.0	80
(M33)	72	78	91	+7.0	85
M36	78	84	97	+8.0	90
(M39)	84	90	103	+8.0	100
M42	90	96	109	+9.0	(105)
(M45)	96	102	115	+9.0	110
M48	102	108	121	+10.0	120
(M52)	—	116	129	+10.0	(125)
M56	—	124	137	+11.0	140
(M60)	—	132	145	+11.0	150
M64	—	140	153	+12.0	160
(M68)	—	148	161	+12.0	170

NOTE Sizes shown in brackets are non-preferred.

Annex E
(informative)
E.1

Basis for the derivation of tolerances

Hexagon bolts and screws

The following figures (Figure E.1 to Figure E.10 inclusive) illustrate the basis for the derivation of tolerances for hexagon bolts and screws.

Figure E.1 Widths across flats

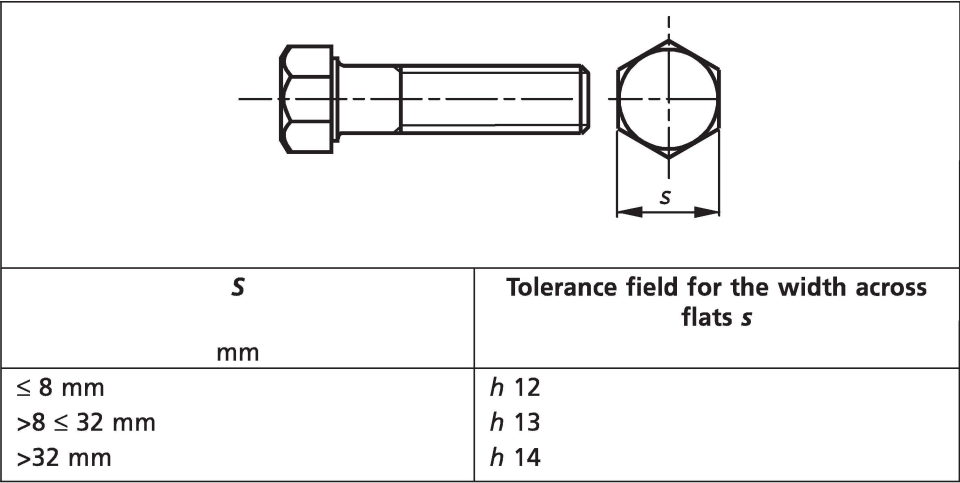


Figure E.2 Widths across corners

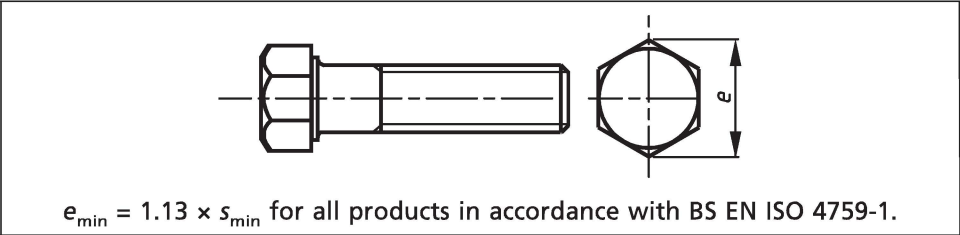


Figure E.3 Heights of heads

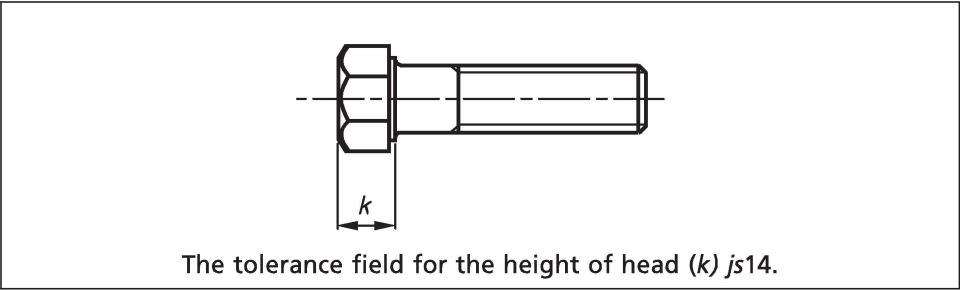


Figure E.4 Shank diameter of full size bolts

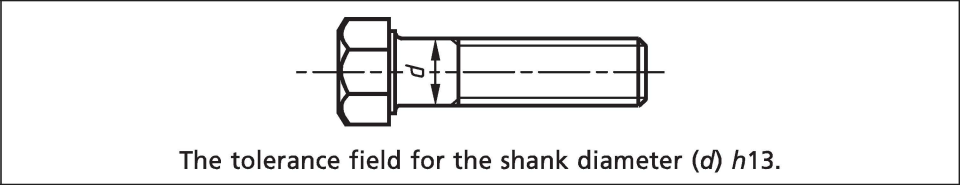


Figure E.5 Nominal length

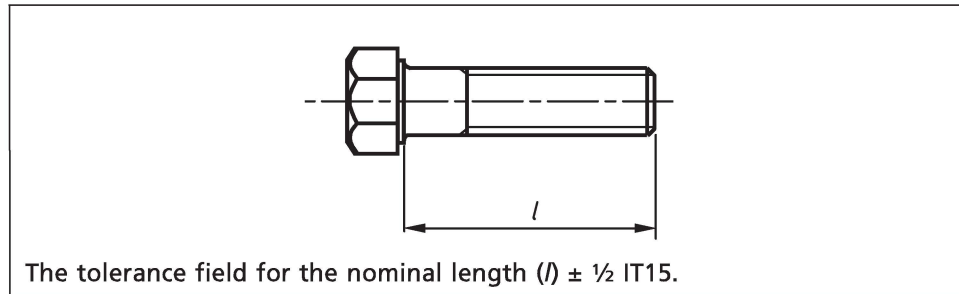


Figure E.6 Thread lengths

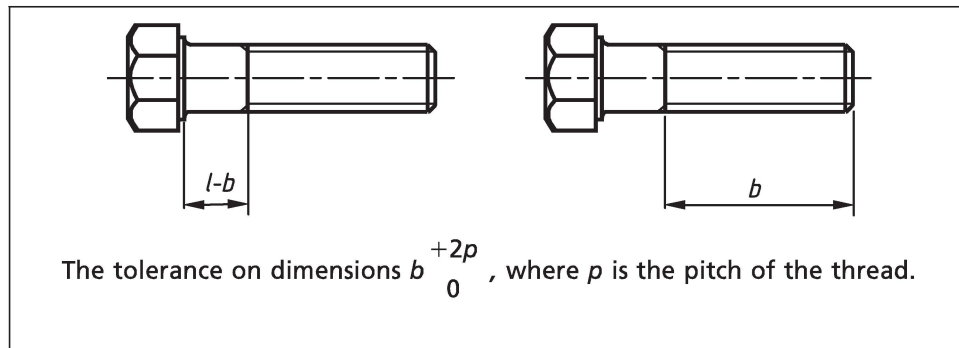


Figure E.7 Eccentricity of the head

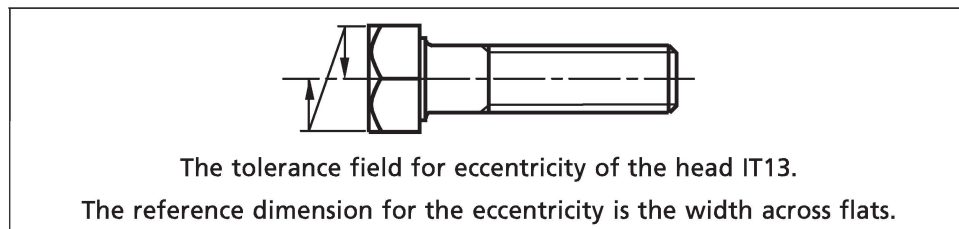


Figure E.8 Angularity of the head

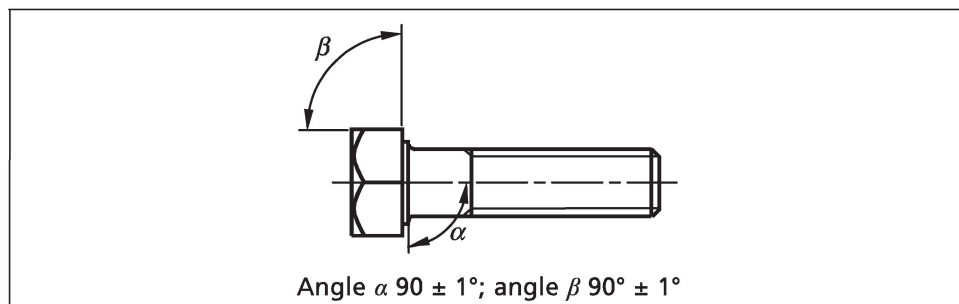


Figure E.9 Eccentricity between shank and thread


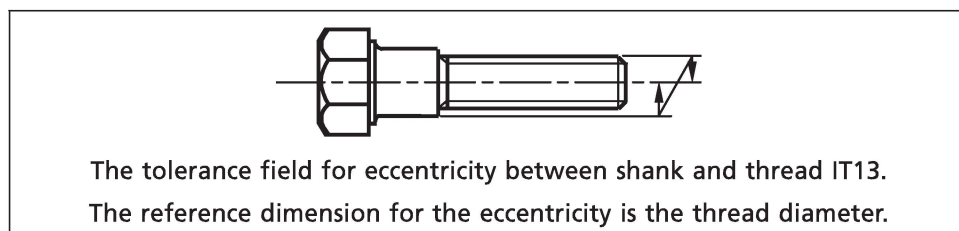


Figure E.10 Eccentricity of split pin hole

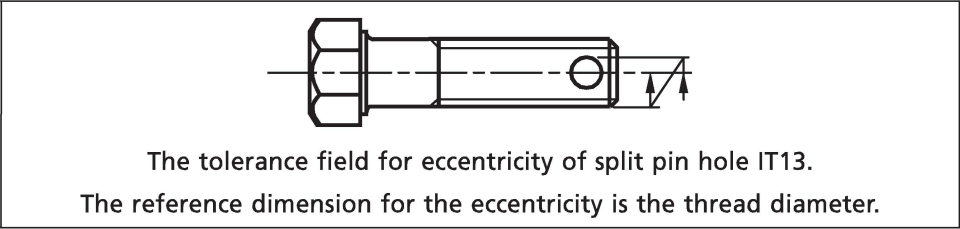

E.2 Hexagon nuts

Figure E.11 to Figure E.17 illustrate the basis for the derivation of tolerances for hexagon nuts.

Figure E.11 Widths across flats

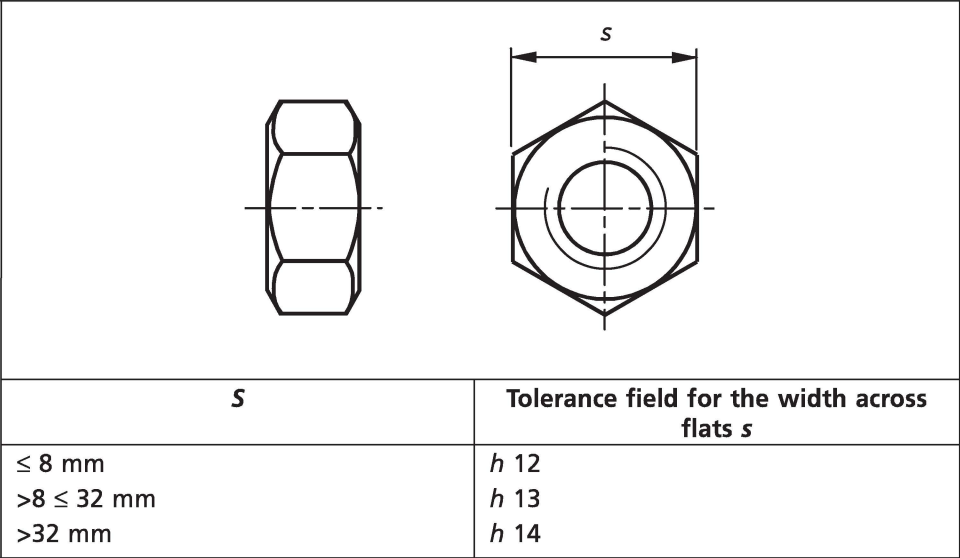


Figure E.12 Widths across corners

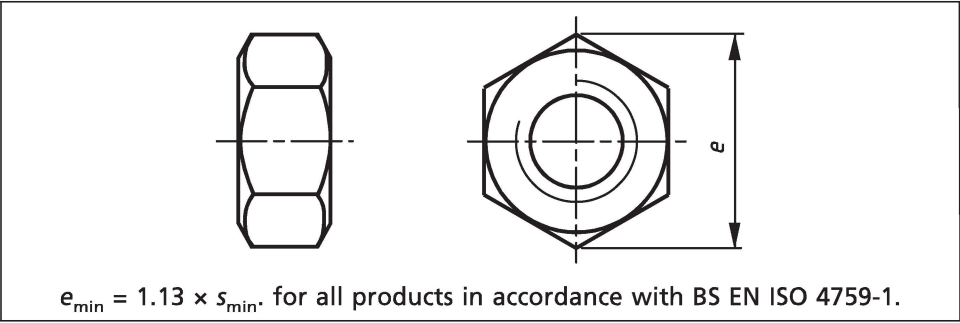


Figure E.13 Thicknesses of nuts

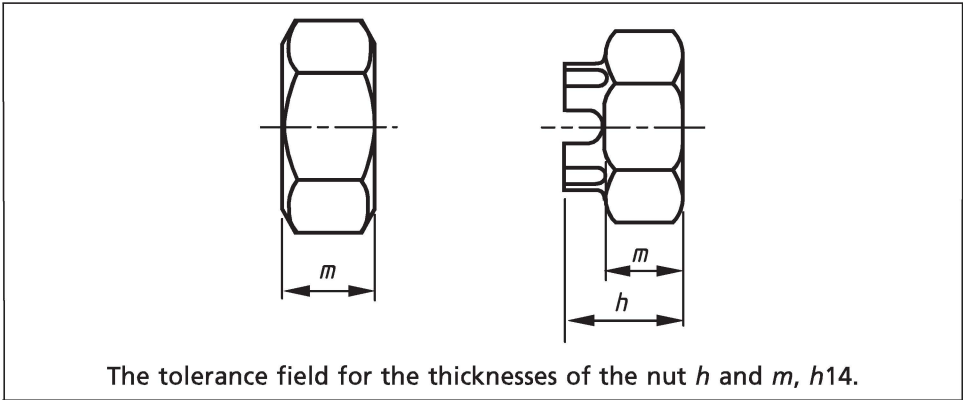


Figure E.14 Dimensions of slots

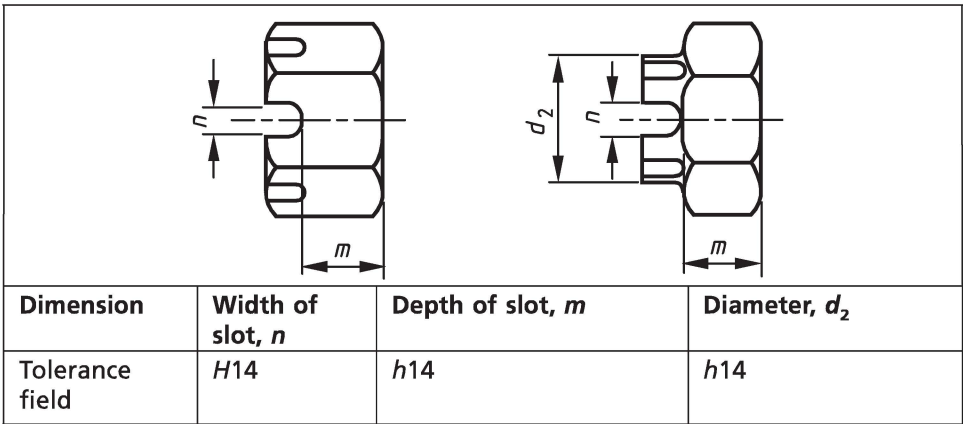


Figure E.15 Eccentricity of the hexagon

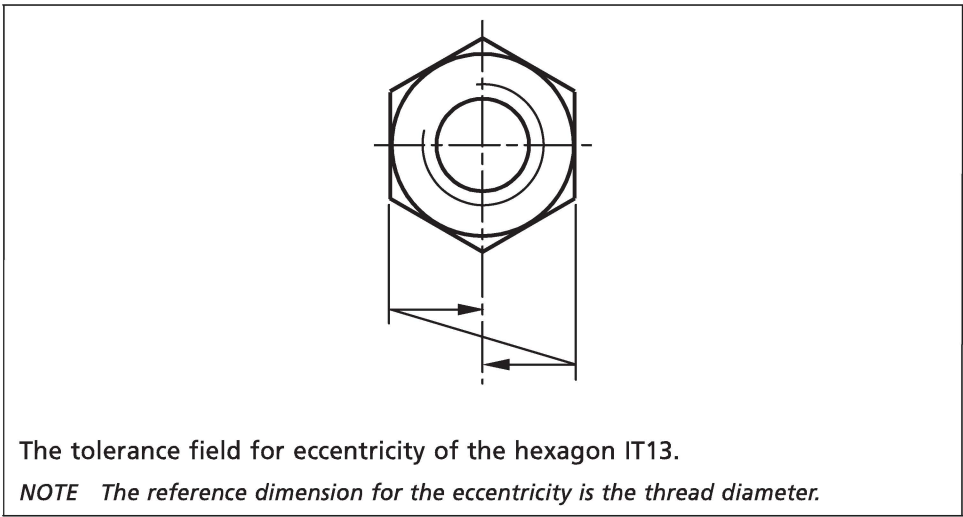


Figure E.16 Eccentricity of the slots


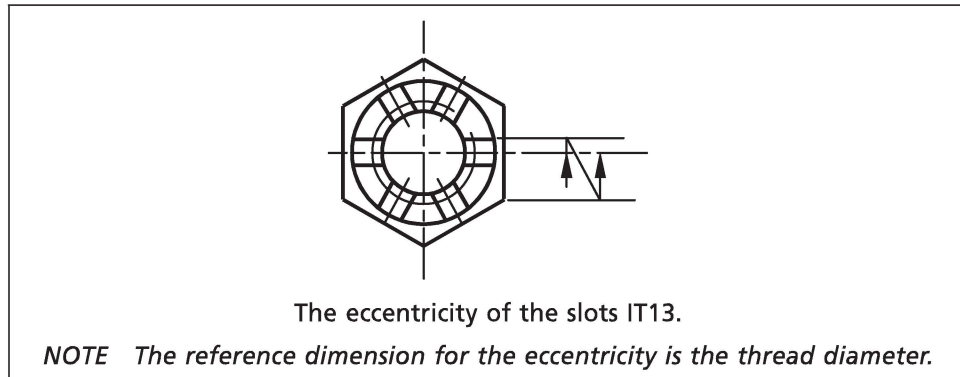


Figure E.17 Angularity of the nuts

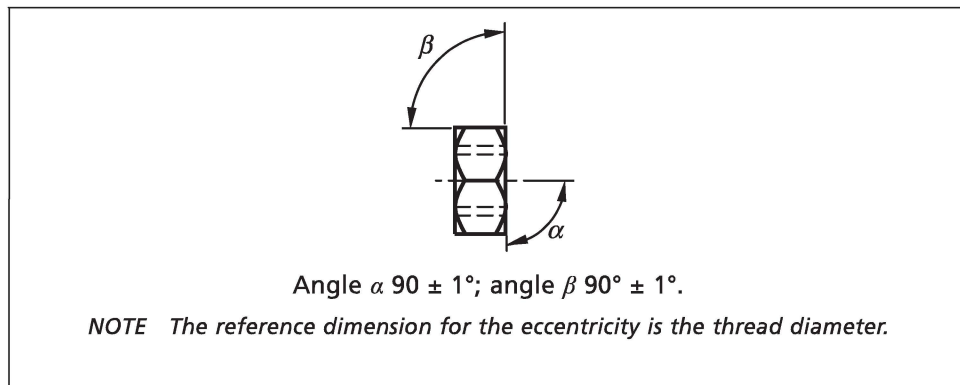

Annex F
(informative)**Manufacturer's recommended range of sizes**

The recommended range of sizes is shown in Table F.1 and Table F.2.

NOTE Depending on popular demand, the sizes stated in Table F.1 and Table F.2 might be revised. It is advisable to consult the supplier about current stock production sizes.

Table F.1 Hexagon head bolts

Nominal length mm	Nominal diameter							
	M5	M6	M8	M10	M12	M16	M20	M24
25	•	•	—	—	—	—	—	—
30	•	•	•	—	—	—	—	—
35	•	•	•	•	—	—	—	—
40	•	•	•	•	•	—	—	—
45	•	•	•	•	•	•	—	—
50	•	•	•	•	•	•	—	—
55	—	•	•	•	•	•	•	—
60	—	•	•	•	•	•	•	—
65	—	•	•	•	•	•	•	•
70	—	•	•	•	•	•	•	•
75	—	•	•	•	•	•	•	•
80	—	—	•	•	•	•	•	•
90	—	—	•	•	•	•	•	•
100	—	—	•	•	•	•	•	•
110	—	—	—	•	•	•	•	•
120	—	—	—	•	•	•	•	•
130	—	—	—	—	•	•	•	•
140	—	—	—	—	—	•	•	•
150	—	—	—	—	—	•	•	•
160	—	—	—	—	—	•	•	•

• Standard thread lengths

Table F.2 Hexagon head screws

Nominal length mm	Nominal diameter							
	M5	M6	M8	M10	M12	M16	M20	M24
10	•	—	—	—	—	—	—	—
12	•	•	—	—	—	—	—	—
16	•	•	•	—	—	—	—	—
20	•	•	•	•	—	—	—	—
25	•	•	•	•	•	—	—	—
30	•	•	•	•	•	•	—	—
35	—	•	•	•	•	•	—	—
40	—	•	•	•	•	•	•	—
45	—	—	•	•	•	•	•	—
50	—	•	•	•	•	•	•	•
55	—	—	—	•	•	•	•	—
60	—	—	•	•	•	•	•	•
70	—	—	—	•	•	•	•	—
80	—	—	—	•	•	•	•	—
• Standard thread lengths								

Bibliography

Standards publications

For dated references, only the edition cited applies. For undated references, the latest edition of the referenced document (including any amendments) applies.

BS 7371-6, *Coatings on metal fasteners – Part 6: Specification for hot dipped galvanized coatings*

BS EN ISO 898-2, *Mechanical properties of fasteners made of carbon and alloy steel – Part 2: Nuts with specified property classes – Coarse thread and fine pitch thread*

BS EN ISO 4032, *Hexagon regular nuts (style 1) – Product grades A and B*

British Standards Institution (BSI)

BSI is the national body responsible for preparing British Standards and other standards-related publications, information and services.

BSI is incorporated by Royal Charter. British Standards and other standardization products are published by BSI Standards Limited.

About us

We bring together business, industry, government, consumers, innovators and others to shape their combined experience and expertise into standards-based solutions.

The knowledge embodied in our standards has been carefully assembled in a dependable format and refined through our open consultation process. Organizations of all sizes and across all sectors choose standards to help them achieve their goals.

Information on standards

We can provide you with the knowledge that your organization needs to succeed. Find out more about British Standards by visiting our website at bsigroup.com/standards or contacting our Customer Services team or Knowledge Centre.

Buying standards

You can buy and download PDF versions of BSI publications, including British and adopted European and international standards, through our website at bsigroup.com/shop, where hard copies can also be purchased.

If you need international and foreign standards from other Standards Development Organizations, hard copies can be ordered from our Customer Services team.

Subscriptions

Our range of subscription services are designed to make using standards easier for you. For further information on our subscription products go to bsigroup.com/subscriptions.

With **British Standards Online (BSOL)** you'll have instant access to over 55,000 British and adopted European and international standards from your desktop. It's available 24/7 and is refreshed daily so you'll always be up to date.

You can keep in touch with standards developments and receive substantial discounts on the purchase price of standards, both in single copy and subscription format, by becoming a **BSI Subscribing Member**.

PLUS is an updating service exclusive to BSI Subscribing Members. You will automatically receive the latest hard copy of your standards when they're revised or replaced.

To find out more about becoming a BSI Subscribing Member and the benefits of membership, please visit bsigroup.com/shop.

With a **Multi-User Network Licence (MUNL)** you are able to host standards publications on your intranet. Licences can cover as few or as many users as you wish. With updates supplied as soon as they're available, you can be sure your documentation is current. For further information, email bsmusales@bsigroup.com.

BSI Group Headquarters

389 Chiswick High Road London W4 4AL UK

Revisions

Our British Standards and other publications are updated by amendment or revision.

We continually improve the quality of our products and services to benefit your business. If you find an inaccuracy or ambiguity within a British Standard or other BSI publication please inform the Knowledge Centre.

Copyright

All the data, software and documentation set out in all British Standards and other BSI publications are the property of and copyrighted by BSI, or some person or entity that owns copyright in the information used (such as the international standardization bodies) and has formally licensed such information to BSI for commercial publication and use. Except as permitted under the Copyright, Designs and Patents Act 1988 no extract may be reproduced, stored in a retrieval system or transmitted in any form or by any means – electronic, photocopying, recording or otherwise – without prior written permission from BSI. Details and advice can be obtained from the Copyright & Licensing Department.

Useful Contacts:

Customer Services

Tel: +44 845 086 9001

Email (orders): orders@bsigroup.com

Email (enquiries): cservices@bsigroup.com

Subscriptions

Tel: +44 845 086 9001

Email: subscriptions@bsigroup.com

Knowledge Centre

Tel: +44 20 8996 7004

Email: knowledgecentre@bsigroup.com

Copyright & Licensing

Tel: +44 20 8996 7070

Email: copyright@bsigroup.com